

Nanoscale

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: A. Elgandy, A. A. Papaderakis, A. Ejigu, K. Helmbrecht, B. Spencer, A. Gross, A. Walton, D. J. Lewis and R. Dryfe, *Nanoscale*, 2024, DOI: 10.1039/D4NR01238K.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Nanosized Chevrel Phases for Dendrite-Free Zinc-Ion Based Energy Storage: Unraveling the Phase Transformations

Amr Elgendy^{a,b,c}, Athanasios A. Papaderakis^{a,b}, Andinet Ejigu^{a,b}, Katharina Helmbrecht^{d,e}, Ben F. Spencer^f, Axel Groß^{d,e}, Alex S. Walton^{a,f}, David J. Lewis^{g*}, Robert A. W. Dryfe^{a,b*}

^aDepartment of Chemistry, University of Manchester, Oxford Road, Manchester, M13 9PL, United Kingdom

^b Henry Royce Institute, University of Manchester, Oxford Road, Manchester, M13 9PL, United Kingdom

^c Egyptian Petroleum Research Institute, 11727, Cairo, Egypt.

^d Institute of Theoretical Chemistry, Ulm University, Albert-Einstein-Allee 11, 89081 Ulm, Germany

^e Helmholtz Institute Ulm (HIU) for Electrochemical Energy Storage, Helmholtzstraße 11, 89081 Ulm, Germany

^f Photon Science Institute, University of Manchester, Oxford Road, Manchester, M13 9PL, United Kingdom

^g Department of Materials, University of Manchester, Oxford Road, Manchester, M13 9PL, United Kingdom

Corresponding Authors

*E-mail: david.lewis-4@manchester.ac.uk Tel: +44 (0) 161-306-3561. (D.J.L.)

*E-mail: robert.dryfe@manchester.ac.uk Tel: +44 (0) 161-306-4522. (R.A.W.D.)

Keywords: Chevrel phase, Mo₆S₈, aqueous zinc ion capacitor, dendrite free, hybrid supercapacitors, multivalent-ion batteries



ABSTRACT

View Article Online
DOI: 10.1039/D4NR01238K

The nanoscale form of the Chevrel phase, Mo_6S_8 , is demonstrated to be a highly efficient zinc-free anode in aqueous zinc ion hybrid supercapacitors (ZIHSCs). The unique morphological characteristics of the material when its dimensions approach the nanoscale result in fast zinc intercalation kinetics that surpass the ion transport rate reported for some of the most promising materials, such as TiS_2 and TiSe_2 . In-situ Raman spectroscopy, post-mortem X-ray diffraction, Hard X-ray photoelectron spectroscopy, and density functional theory (DFT) calculations were combined to understand the overall mechanism of the zinc ion (de)intercalation process. The previously unknown formation of the sulfur-deficient $\text{Zn}_{2.9}\text{Mo}_{15}\text{S}_{19}$ ($\text{Zn}_{1.6}\text{Mo}_6\text{S}_{7.6}$) phase is identified, leading to a re-evaluation of the mechanism of the (de)intercalation process. A full cell comprised of an activated carbon (YEC-8A) positive electrode, delivers a cell capacity of 38 mAh/g and an energy density of 43.8 Wh/kg at a specific current density of 0.2 A/g. The excellent cycling stability of the device is demonstrated for up to 8000 cycles at 3 A/g with a coulombic efficiency close to 100%. Post-mortem microscopic studies reveal the absence of dendrite formation at the nanosized Mo_6S_8 anode, in stark contrast to the state-of-the-art zinc electrode.

1. Introduction

Electrochemical systems, including batteries, supercapacitors, and hybrid devices (also known as “supercapatteries”), are set to play an increasing role in storage of electricity generated from renewable sources such as solar, wind, and tidal inputs.^{1–3} Lithium-ion batteries (LIB) continue to dominate the energy storage market, due to their high energy density.⁴ There are, however, increasing concerns about the sustainability of LIBs: the use of highly flammable organic electrolytes leads to safety challenges. Additionally, the uneven distribution of lithium resources has encouraged the development of post-LIB systems.⁴ One promising alternative is the use of zinc-based energy storage devices with mild aqueous electrolytes for grid-level energy storage. These devices have the advantages of simple manufacturing, high theoretical capacity (820 mA h g^{-1}), abundant and low-cost raw materials, as well as higher intrinsic safety.^{5,6} In recent years, there has been significant progress towards the development of cathode materials that deliver high energy density in zinc-based energy storage devices. In particular, manganese-based materials, various organic (e.g., quinone derivatives, conductive polymers and dyes) as well as inorganic (e.g., Prussian blue analogues) hosts and vanadium-



based ionic conductors (e.g., NASICON) have been reported as highly efficient cathodes for zinc-ion batteries (ZIBs).^{2,7,8} In parallel, several types of activated carbon have been effectively used as cathodes in zinc-ion hybrid supercapacitors (ZIHSCs). However, all of these devices require a bulk zinc electrode as anode to compensate for the issues of dendrite growth and corrosion, which lead to low coulombic efficiency during the zinc plating/stripping process.⁷ As a result, the actual energy and power densities of most zinc-ion batteries and supercapacitors are significantly lower than their theoretical values. In addition, aqueous zinc-ion energy storage devices often exhibit poor cycling stability due to the high rate of hydrogen gas evolution produced by the parasitic process of water splitting over the zinc metal anode.⁹ Consequently, it becomes evident that the use of metallic zinc anodes poses serious challenges. Currently, there are ongoing efforts to suppress the formation of Zn dendrites by using electrolyte additives, establishing an artificial solid electrolyte interphase (SEI) layer, and alloying Zn with other transition metals such as Cu.^{10,11} However, these approaches have their own drawbacks, namely increased battery cost and decreased specific and volumetric energy density in the case of electrolyte additives, instability issues of the deposited film when using an artificial SEI layer and reduced specific capacity for Zn-alloy anodes due to the decrease of the Zn active constituents upon alloying.

Based on the acquired knowledge from lithium metal batteries, it is of paramount importance to develop a zinc metal-free anode that can reversibly intercalate/de-intercalate Zn ions and hence potentially address the Zn dendrite issue.¹² Ideal intercalation anodes should have low intercalation potential vs. Zn^{2+}/Zn , be electrochemically stable during charging/discharging, have good electronic conductivity, and high capacity. Currently, there are few materials that have shown the ability to intercalate Zn ions. These include layered-2D titanium disulfide (TiS_2) with an intercalation potential of 0.4 V vs. Zn^{2+}/Zn in aqueous electrolyte¹³, $TiSe_2$ with a sloping discharge plateau at +0.35 V vs. Zn^{2+}/Zn and a discharge capacity of ~63 mAh/g at 0.3 A/g⁷, as well as hexagonal MoO_3 that exhibits a discharge potential of ~-0.37 V (vs. Zn^{2+}/Zn) and a discharge capacity of 80 mAh/g at 0.5 A/g.¹⁴ However, potential zinc-ion-free anodes are not limited to inorganic materials; organic hosts such as carbonyl-rich molecules (perylene-tetracarboxylic dianhydride or PTCDA, and perylene-tetracarboxylic diimide or PTCDI) demonstrate promising characteristics as anodes.¹⁵ There are major disadvantages associated with these materials, including their significantly lower electrical conductivity compared to the inorganic alternatives, limited cycling stability, high discharge potential (vs. Zn^{2+}/Zn) and/or low discharge capacity, which severely limit their use in practical systems.



As a host material for different mono/multivalent ions, Chevrel phases (CPs), $M_6Mo_6T_8$ (M = metal; T = S, Se, or Te), are appealing because of their characteristic chemical intercalation properties for lithium, sodium, magnesium, calcium, manganese, iron, cobalt, nickel, and zinc.^{16–18} CPs exhibits a relatively low discharge potential of 0.32 V *vs.* Zn^{2+}/Zn , being the lowest reported among Zn-free anode candidates. However, the low cycle stability, possibly due to the micro-sized structure of the prepared material, impedes its wider use.¹⁹ Recently, our group reported the facile, rapid and highly controllable synthesis of nanostructured CPs. The unique structural characteristics of the prepared material in combination with its high electrical conductivity renders it a promising anode material, exhibiting fast lithium ion (de)intercalation kinetics and high cycling stability.^{20,21}

Inspired by the compelling physicochemical properties of the nano-sized Mo_6S_8 , we explore its applicability as a Zn-free negative electrode for ZIHSC. It is worth mentioning that to the best of our knowledge, there are no previous reports on the use of CPs as an anode material in ZIHSC. On this basis, a complete and systematic physicochemical study of CPs electrochemistry in zinc electrolytes has been conducted. Most notably, the formation of the sulfur-deficient phase $Zn_{2.9}Mo_{15}S_{19}$ has been identified, providing novel insights into the long-standing debate of Zn-ion trapping. With this knowledge, we have developed a ZIHSC with a nano-sized structure (de)intercalation battery-type anode and activated carbon (AC) double layer capacitance-type cathode using a 2 M $ZnSO_4$ aqueous electrolyte. When compared with the traditional hybrid supercapacitor where zinc metal serves as the anode, the developed device has the following merits: a) the use of a Zn-free anode prevents dendrite formation during the charge/discharge process and thus increases the coulombic efficiency while simultaneously reducing safety risks, b) fast zinc ion diffusion into the Mo_6S_8 cavities as evidenced by means of the galvanostatic intermittent titration technique (GITT) renders the Mo_6S_8 anode compatible with the AC cathode, c) the use of aqueous $ZnSO_4$ electrolyte is cost-effective and “eco-friendly”, in contrast to the organic electrolytes commonly used. The Mo_6S_8 showed a multistep zinc ion (de)intercalation process with an average discharge potential of ~ 0.32 V *vs.* Zn^{2+}/Zn , and reversible discharge capacity of ~ 66 mAh/g at the current density of 0.1 A/g. As a result, the assembled ZIHSC achieves a high capacity of ~ 38 mAh/g (0.2 A/g) and a superior energy density of 43.8 Wh/kg. Notably, the power density remains as high as 2500 W/kg and the energy density is maintained at 25 Wh/kg when the current density is increased to 2 A/g. Moreover, the device shows extended cycle life of up to 8000 cycles at a moderate current density of 3 A/g. Furthermore, microscopic studies of the cycled electrode revealed the complete absence of zinc dendrites.



2. Experimental Section and methods

2.1 Material and methods

Molybdenum(0) powder (1–5 μm , $\geq 99.9\%$), molybdenum(0) hexacarbonyl (98%), tetraethylthiuram disulfide ($\geq 97\%$), zinc sulfate heptahydrate ($\geq 99\%$) and zinc chloride ($\geq 98\%$) were purchased from Sigma-Aldrich. Copper(II) dibutyldithiocarbamate ($>98\%$) was purchased from Tokyo Chemical Industry (UK) Ltd. The activated carbon (AC, grade YEC-8 A) was purchased from Fuzhou Yihuan Carbon Co., Ltd (China). Ultrapure water (resistivity = 18.2 $\text{M}\Omega\text{ cm}$, Milli-Q Direct 8) was used in all electrochemical studies. All the chemicals were used without further treatment.

2.2 Synthesis of $\text{Cu}_2\text{Mo}_6\text{S}_8$ nanocubes.

The synthesis of $\text{Cu}_2\text{Mo}_6\text{S}_8$ was carried out according to our previous reports and is schematically illustrated in Figure S1.^{20,21} Briefly, stoichiometric amounts of tetrakis(diethyldithiocarbamate) molybdenum (IV) (1.4 g, 2 mmol), Mo (0.2 g, 2 mmol), and copper (II) dibutyldithiocarbamate, (0.5 mg, 1.3 mmol) powders were thoroughly mixed using a pestle and mortar. All powders were then compressed into pellet form, with a diameter of 11 mm, using a hydraulic press at 20 tonnes to ensure better homogeneity and avoid phase separation. The pellet was centred in a ceramic boat inside a tube furnace and the system was purged with argon gas for 20 minutes. Finally, the temperature was gradually increased to 800 $^\circ\text{C}$ (3 $^\circ\text{C}/\text{min}$) and kept under Ar for 7 hours at this temperature. Subsequently, the prepared $\text{Cu}_2\text{Mo}_6\text{S}_8$ powder was dispersed and stirred for 10h in 6 M HCl solution (Fisher Scientific, Inc.). The solution was purged with oxygen to facilitate Cu leaching. The solution was centrifuged, and the resulting material was washed several times with de-ionized water and dried at 80 $^\circ\text{C}$ overnight to obtain Mo_6S_8 . Furthermore, it is worth mentioning that copper can be successfully leached electrochemically from the neat Chevrel phase (a detailed process can be found in the supplementary information (Figure S2)).

2.3 Material Characterisation

The structure of the prepared materials was investigated by powder X-ray diffraction (P-XRD) using an XRD5-PANalytical X'Pert Pro diffractometer with Cu $K\alpha$ radiation ($\lambda=1.5406\text{ \AA}$) operating at 40 kV. The (2 θ) data were recorded in the range of 10 $^\circ$ to 80 $^\circ$. The morphology of the active materials was analysed with a field-emission scanning electron microscope (FE-SEM, Quanta 650) equipped with energy-dispersive X-ray (EDX) at 15kV. The sample was dried and then placed over a conductive carbon tape substrate. The Raman spectra were recorded using a Renishaw inVia Confocal microscope with a 523 nm excitation laser operated



at a power of 0.274 mW with a grating of 1800 lines/mm and 50 \times objective. The *in-situ* Raman cell was purchased from ECC-Opto-Std (EL-Cell GmbH, Hamburg, Germany). The cell comprised of a free-standing Mo₆S₈ film (positive electrode) pressed on a titanium foil substrate that contained a small hole in its middle (diameter ca. 1 mm). A glass membrane (7 mm diameter) soaked with 2 M ZnSO₄ electrolyte was used as a separator and zinc metal as a counter and reference electrode. The laser beam was shone through a small hole in the centre of the Ti substrate that was covered with a thin glass window on the back of the free-standing Mo₆S₈ film. The Raman spectra were collected at various voltages during the charging/discharging process at 1 mV/s. Hard X-ray Photoelectron Spectroscopy (HAXPES) was performed using monochromated Ga K α metal jet X-ray radiation (9252 eV, 3.57 mA emission at 250 W, micro-focussed to 50 μ m) and an EW-4000 high voltage electron energy analyser (HAXPES-Lab, Scienta Omicron GmbH); the instrument has a base vacuum pressure of 5×10^{-10} mbar.^{22,23} The entrance slit width used was 1.5 mm, and the pass energies used for survey and core level spectra were 500 and 100 eV respectively, with total energy resolutions of 2.0 and 0.6 eV respectively, as measured using the FWHM of the Au 4f_{7/2} core level on a clean gold reference sample.²² The HAXPES instrument also has a monochromated Al K α X-ray source (1486 eV, 20 mA emission at 300 W) for surface-sensitive XPS at the same sample position. Charge neutralisation for insulating samples is achieved using a low energy electron flood source as required (FS40A, PreVac). Binding energy (BE) scale calibration was performed using Au 4f_{7/2} at 84 eV of a clean gold reference sample, otherwise C 1s at 284.8 eV BE, if the flood source was used. Analysis and curve fitting was performed using Voigt-approximation peaks using CasaXPS.²⁴ Core level relative sensitivity factors for HAXPES quantification were calculated according to previous reports.^{23,25}

2.4 Electrochemical characterisation

The zinc storage performance of the prepared Mo₆S₈ was tested in a three-electrode configuration. The working electrode was prepared by mixing 9 mg of active material with 1 mg of carbon black ("Super P", supplied by Alfa Aesar, 99+% metals basis). The mixed powder was then dispersed in 1 ml of a 4:1 water/ethanol mixture, followed by addition of 45 μ L of Nafion® solution. The suspension was sonicated for 1h to yield a homogenous ink. A specific amount of this ink was drop-cast on a polished glassy carbon (GC) substrate with a geometric area of 0.0707 cm². The total mass loading of each electrode was approximately 1.08 mg/cm². For electrochemical testing, Ag/AgCl (3.5 M KCl) and Pt mesh were used as the reference and counter electrodes, respectively. 2 M ZnSO₄(aq) bubbled, with N₂ gas for 30 min, was used as the electrolyte. Note that although the three-electrode measurements were conducted using an



Ag/AgCl reference electrode, for ease of comparison of three-electrode and coin cell data, all potentials are reported with respect to Zn^{2+}/Zn (both scales are given in the relevant graphs in the SI)

For ZIHSC device assembly, the negative electrode, Mo_6S_8 , was prepared by mixing the active material, “Super P” and polytetrafluoroethylene binder (60 wt% in water, Aldrich) in a weight ratio of 8.0:1.0:1.0 to obtain a homogeneous free-standing slurry with the help of ethanol. Then the film was evenly pressed onto a stainless steel grid (grade 316) and used as the anode. For the positive electrode, activated carbon (YEC-8A), “Super P”, and polyvinylidene fluoride were mixed in 2 ml of N-Methyl-2-pyrrolidone (NMP) with a mass ratio of 8.0:1.0:1.0 to obtain a homogenous slurry. After that, the slurry was coated on a titanium substrate and dried at 100 °C overnight for further use. The electrochemical performance of the AC electrodes was tested in half-cell devices, i.e., the AC was used as the working electrode, 2 M ZnSO_4 was used as the aqueous electrolyte, and zinc plate (14 mm) was used as the counter and reference electrode. In a similar design, the galvanostatic intermittent titration technique (GITT) was used to study the solid-state diffusion of zinc ions into the Mo_6S_8 crystal structure. The measurements were performed at a current density of 0.1 A/g for 15 sec and a relaxation of 150 sec. The ZIHSC was assembled in a CR2032-type coin cell using a hydraulic crimper (MSK-160D) with a Mo_6S_8 anode (3-5.8 mg/cm²), AC cathode (5.3-9.7 mg/cm²), and glass membrane used as the separator. In all electrochemical experiments, cyclic voltammetry (CV) measurements were carried out with Metrohm PGSTAT302N potentiostat, equipped with the FRA32 module and controlled via Nova 1.11 software. The galvanostatic charge/discharge tests (GCD) were recorded with a voltage range from 0 V to 1.6 V at different current densities, and the cyclic stability was carried at a current density of 3 A/g for 8000 cycles. Both (GCD), and GITT measurements were performed on a Battery Test System (BaSyTec GmbH, Germany) at room temperature.

2.5 Computational details

The properties of the CP and similar structures were studied using periodic density functional theory,^{26–28} as implemented in the Vienna Ab initio Simulation Package.^{29–31} To account for exchange and correlation, the generalized gradient approximation in the formulation of Perdew, Burke and Ernzerhof (PBE)³² has been used. The electron-core interactions are represented by the Projector Augmented Wave (PAW)³³ method. Calculations were first performed for the Mo_6S_8 unit cell of the CP with the Brillouin zone sampled using a $4\times 4\times 4$ k-point grid. For other unit cells the k-point grid was scaled accordingly in each lattice direction to achieve the same density. The $\text{Zn}_{2.9}\text{Mo}_{15}\text{S}_{19}$ was analyzed in its symmetry-reduced unit cell, which contains two



formula units. The electronic structure was converged to 1×10^{-5} eV, applying a plane-wave cutoff energy of 450 eV. All formation energies with respect to the insertion of the Zn atoms are determined with respect to the Zn metal bulk energy. Hence a positive formation energy means that the insertion is not stable with respect to the formation of the bulk metal.

3. Results and Discussion

3.1 Synthesis of Mo_6S_8

The prepared Mo_6S_8 phase was confirmed with powder X-ray diffraction. Figure S3 shows that the diffraction pattern of the prepared Mo_6S_8 is well matched with the standard Mo_6S_8 (ICSD#252376). Moreover, the presence of a strong peak at 13.8° associated with the (101) plane and the minimal appearance of the peak at 14.4° being indexed to MoS_2 , confirms the high purity of the synthesised Mo_6S_8 compound. These values are in good agreement with previous reports,^{18,34} demonstrating that the material was successfully synthesized. Full characterisation of the Mo_6S_8 prepared with the molecular precursor approach, including XRD, Rietveld refinement, Raman spectroscopy, and morphological characterisation via SEM and EDX can be found in our previous work.^{20,21}

3.2 Storage behavior of zinc ions in Mo_6S_8

The electrochemical properties of zinc intercalation into Mo_6S_8 were thoroughly investigated in a three-electrode system. The Mo_6S_8 material shows two distinguishable quasi-reversible reduction and oxidation peaks related to the zinc intercalation/deintercalation process (Figure 1(a, b)) according to the following equations:¹⁹



The Zn^{2+} insertion process was found to follow a multistep intercalation mechanism whereby $\text{Zn}_x\text{Mo}_6\text{S}_8$ is initially formed at a potential of approximately ~ 0.5 V vs Zn^{2+}/Zn (equation 1) with its subsequent transformation to $\text{Zn}_2\text{Mo}_6\text{S}_8$ at around ~ 0.3 V vs Zn^{2+}/Zn as Zn^{2+} are further inserted into the Mo_6S_8 cavities (equation 1). This observation is consistent with previous work by Yingwen et al.³⁵, as presented in their supplementary data (Figure S2 of reference 35). A noteworthy feature of Figure 1a is that during the second cycle, the position of the cathodic insertion peak shifts from ~ 0.38 V to approximately ~ 0.5 V vs Zn^{2+}/Zn , and the peak current is significantly reduced. Following that, as the number of cycles proceeds, the peak position and current remained roughly unchanged. On first sight, this might be related to zinc ion trapping during the Zn_x formation: this process was reported by Aurbach et al.³⁶ for CPs prepared with micro-sized structure, although they did not thoroughly investigate the composition or properties of the phase that formed as a result of this process.



The intercalation of zinc into Mo₆S₈, was confirmed by testing bare and modified Mo₆S₈ GC electrodes in 2 M ZnSO₄ (Figure S4). It is clear that the redox peaks shown in Figure S4b, and Figure 1a are due to the zinc intercalation/de-intercalation process and not due to the zinc plating/stripping process. In order to further investigate the electrochemical kinetics of Mo₆S₈ towards zinc ions, a series of cyclic voltammetry tests were recorded at different scan rates. Figure 1b shows that the cathodic and anodic peaks slightly shift with increase of scan rate from 0.5 to 5 mV/s, due to increased polarization with higher sweep rates, a phenomenon that is associated with battery-type electrode materials.^{7,20} To study the zinc ion energy storage mechanism in detail, the relationship between the peak current (I) and scan rate (ν) was investigated based on the power-law formula $I = a \nu^b$, where the value of the exponent b (the slope of $\log(I)$ vs. $\log(\nu)$ plot), provides information about the charge storage mechanism. For a diffusion-controlled process, I is proportional to the square root of ν ($b = 0.5$). However, for processes that involve surface ion adsorption/desorption, the current response is proportional to the scan rate ($b = 1$).²⁰ As seen in Figure 1c, the results from $\log(I)$ and $\log(\nu)$ show that the calculated b values are *ca.* 0.50, and 0.58 for zinc intercalation and de-intercalation, respectively, suggesting that the zinc storage mechanism into nanosized Mo₆S₈ is controlled by diffusion. The charge/discharge behaviour of zinc ions in the electrode was evaluated in a two-electrode coin cell system comprised of Mo₆S₈ as working electrode, 2 M ZnSO₄ as electrolyte, and Zn foil as counter and reference electrode. The observations of the galvanostatic charge-discharge shown in Figure 1d were consistent with those of the CV, in which two voltage plateaus are clearly observed. In particular, an ill-defined shoulder is recorded in the higher voltage region at *ca.* ~0.53 V vs Zn²⁺/Zn followed by a clear plateau at ~0.34V vs Zn²⁺/Zn. The electrode shows a capacity of 66 mAh/g at current density of 0.1 A/g (~0.8 C), which decreases to 35 mAh/g, as the current density increases to 0.3 A/g (2.4C).



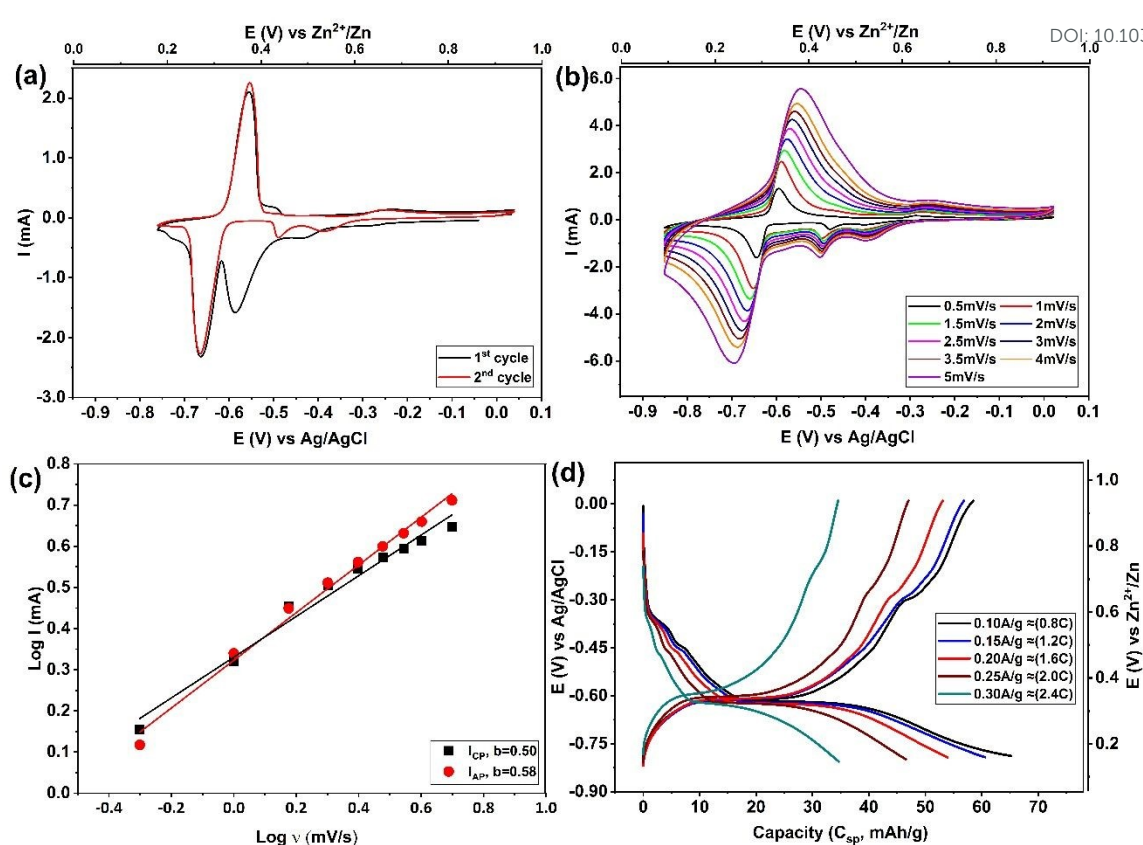


Figure 1. Electrochemical studies on Zn-ion intercalation into Mo₆S₈ electrode in 2M ZnSO₄. (a) Cyclic voltammetry profiles of the 1st and 2nd cycles recorded at 1 mV/s, and (b) CV recorded at different scan rates from 0.5 to 5 mV/s. (c) The log(I) versus log(v) plots of the main peak located at ~0.25 V vs Zn²⁺/Zn in CV curves. (d) The GCD (voltage-capacity) profiles recorded at different current density. Here, the 1 C rate was calculated as 128 mA/g based on the theoretical capacity of the four-electron reaction from Mo₆S₈ to Zn₂Mo₆S₈.

In order to provide insights into the rather uncharted phenomenon of zinc trapping, we investigate the effect of (electro)chemical parameters, i.e., electrolyte identity and applied potential bias, on the overall process. Figure S5 shows the CVs derived from the experimental protocol adopted for the data presented in Figure 2(a,b), using two other zinc electrolytes, namely 2M ZnCl₂ and saturated zinc triflate (Zn(OTf)₂). From the observed response, it is evident that zinc trapping is practically unaffected by the anion identity. The influence of the cathodic potential limit is shown in Figure S6. It was found that even when the latter is confined to potentials more positive than the second step in the previously proposed reaction scheme (equation 1), the position and magnitude of the peak attributed to zinc trapping remains



unchanged. Both findings strongly suggest that trapping of Zn ions in the Mo_6S_8 cavities is related to the intrinsic properties of the host material.

The intercalation of Zn^{2+} ions into Mo_6S_8 nanocubes was investigated with ex situ post-mortem X-ray diffraction (XRD) on cycled electrodes. Initially, the Mo_6S_8 electrode was charged and discharged at a rate of 0.1 A/g. In the second step, the electrodes were removed from the Zn/ Mo_6S_8 half-cell, washed thoroughly with de-ionized water, and dried before the XRD measurements were recorded. In the XRD pattern of the charged Mo_6S_8 presented in Figure 2, four peaks of high intensity can be seen at $2\theta = 10.7^\circ$, 12.4° , 18.2° , and 21.4° : these closely match the standard XRD pattern of the sulfur-deficient phase of $\text{Zn}_{2.9}\text{Mo}_{15}\text{S}_{19}$ ($\text{Zn}_{1.16}\text{Mo}_6\text{S}_{7.6}$, ICSD#601649). These peaks are distinct from the ZnMo_6S_8 (ICSD#252375) and $\text{Zn}_2\text{Mo}_6\text{S}_8$ (ICSD#252374) phases, indicating the formation of the $\text{Zn}_{1.16}\text{Mo}_6\text{S}_{7.6}$ phase upon Zn intercalation³⁵. Although Rietveld refinement was not possible on the data shown in Figure 2 due to the broad nature of the peaks, we were able to perform Rietveld refinement of the diffraction data from another coin cell sample with stronger and sharper X-ray reflections (Figure S7). The results indicate that one of the crystalline products is $\text{Zn}_{1.16}\text{Mo}_6\text{S}_{7.6}$, which is produced as a mixture with a small side-product of $\text{Zn}_4(\text{OH})_6(\text{SO}_4)\cdot 5\text{H}_2\text{O}$.

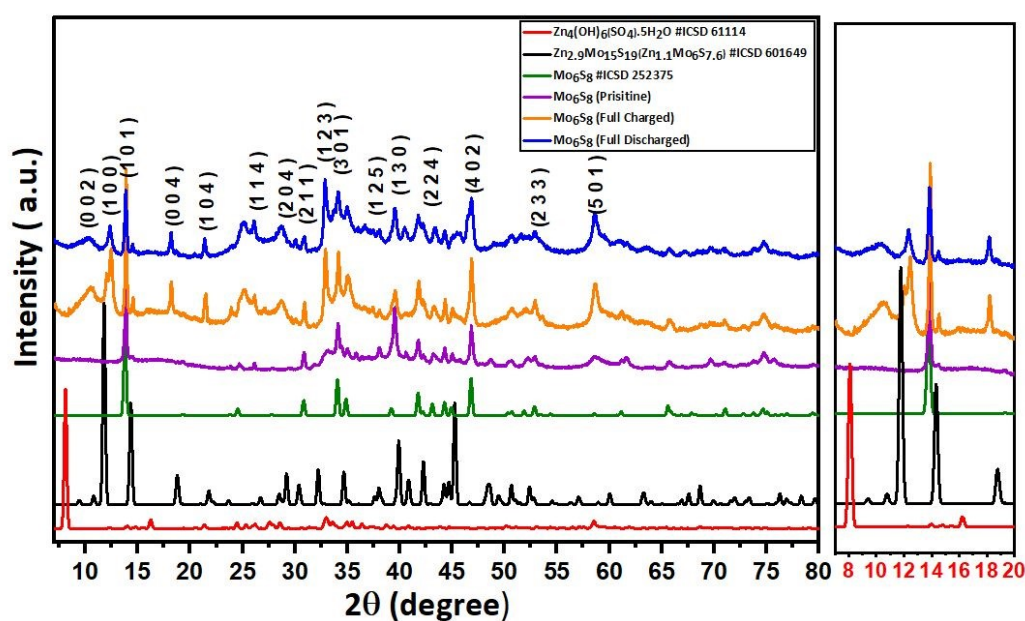


Figure 2. Post-mortem powder-XRD pattern recorded on the pristine, fully charged to 0.15 V vs Zn^{2+}/Zn , and fully discharged to 1 V vs Zn^{2+}/Zn Mo_6S_8 electrode, along with the standard pattern of Mo_6S_8 (ICSD#252376), $\text{Zn}_4(\text{OH})_6(\text{SO}_4)\cdot 5\text{H}_2\text{O}$ (ICSD#61114), and $\text{Zn}_{2.9}\text{Mo}_{15}\text{S}_{19}$ (ICSD#601649).



In the fully discharged state, the sharp crystalline peaks at $2\theta = 10.7^\circ$, 12.4° , 18.2° , and 21.4° resulting from Zn^{2+} insertion are still evident, albeit with reduced intensity. This finding demonstrates that zinc is trapped within the Mo_6S_8 structure, and the Mo_6S_8 structure is not fully recovered.

It is worth noting that the $\text{Zn}_{1.16}\text{Mo}_6\text{S}_{7.6}$ phase we observe is distinct from the zinc hydroxide sulfate phases e.g. $\text{Zn}_4(\text{OH})_6\text{SO}_4 \cdot 0.5\text{H}_2\text{O}$ and $\text{Zn}_4(\text{OH})_6(\text{SO}_4) \cdot 5\text{H}_2\text{O}$, which are observed when zinc metal is used as the electrode material in Zn- MnO_2 batteries or Zinc hybrid supercapacitors. This hypothesis is supported by comparing the experimental XRD data of both the charged and discharged Mo_6S_8 samples with the standard XRD diffraction pattern of the zinc basic sulfate pattern, and the Rietveld refinement on the highly crystalline sample. Typically, the formation of the zinc hydroxide sulfate phase is a result of localized pH changes, caused by H^+ insertion in the MnO_2 during the discharge process, which leads to an increase in OH^- concentration and thus, the formation of flakelike product of zinc hydroxide sulfate hydrate ($\text{Zn}_4(\text{OH})_6(\text{SO}_4) \cdot 5\text{H}_2\text{O}$) on the surface of MnO_2 ³⁷. It is also known that the zinc hydroxide sulfate phase undergoes a reversible precipitation/dissolution process during the charge/discharge process. On the contrary, this reversibility is not observed in the $\text{Zn}_{1.16}\text{Mo}_6\text{S}_{7.6}$ phase. This is evident as the peaks corresponding to $\text{Zn}_{1.16}\text{Mo}_6\text{S}_{7.6}$ are consistently identifiable in both the fully charged and discharged samples within the XRD patterns, albeit with different intensity.

The surface and chemical composition of Mo_6S_8 was examined with *ex situ* hard X-ray photoelectron spectroscopy (HAXPES, 9252 eV) in combination with conventional XPS (1486 eV) during the zinc ions' intercalation and (de)intercalation processes (Figure 3). The higher sampling depth of HAXPES, being ca. 43 nm based on the Mo 2p core level in the Mo_6S_8 sample, enables it to probe the structure of the material more deeply than conventional XPS (with a sampling depth of ca. 5 nm). Consequently, HAXPES can provide information about the physicochemical characteristics of the material at deeper sampling depth, in addition to the outermost surface layers. By comparing the data recorded using the two photon energies we are able to monitor any changes occurring on the surface and sub-surface of Mo_6S_8 during the zinc ions' (de)intercalation process. In addition, HAXPES allows the use of deeper core levels at relatively higher binding energies, such as S 1s (~2469 eV BE). Figure 3(a,b) displays the narrow-window Mo 3d/S 2s core level scans of the blank CP sample (the electrode where no (de)intercalation process occurred), recorded using XPS and HAXPES techniques. Mo 3d_{5/2} photoelectron peaks are present at 228 eV corresponding to the Mo^{2+} oxidation state, and 229.1



corresponding to the Mo^{3+} oxidation state in Mo_6S_8 , which agrees with earlier reports.³⁴ Furthermore, the XPS and HAXPES data shows the presence of an additional peak ~ 232.5 indicating the presence of an oxide surface film corresponding to the Mo^{6+} oxide state. These results suggest that the oxides are located on the surface of the sample, which could be attributed to the exposure of the sample to ambient air prior to the measurements. However, upon zinc insertion into the Mo_6S_8 the narrow window spectrum of the Mo 3d/S 2s core levels tend to change significantly as a function of the insertion potential (0.5 V and 0.3 V vs Zn^{2+}/Zn), indicating the successful insertion of the ions into the Mo_6S_8 structure. Furthermore, upon the insertion of Zn^{2+} ions, the binding energy experiences a shift towards higher energy levels in comparison to the pristine Mo_6S_8 . This shift in both XPS and HAXPES data indicates that the $[\text{Mo}_6]^m$ cluster, where m represents the number of electrons involved in the formation of metallic bonds within the pristine Mo_6 cluster, is oxidized to $[\text{Mo}_6]^{m-n}$, where n with values between 0 and 1 denotes the number of electrons lost. This abnormal oxidation of Mo differs from the typical reduction of transition metals observed in conventional cathode materials upon cation insertion.³⁸ This finding is also consistent with the observation made when Al^{3+} was inserted into Mo_6S_8 using an ionic liquid electrolyte.³⁹ The XPS spectra also show another species with Mo 3d_{5/2} at ~ 234 eV, which we assign as a higher oxide state that could include MoO_x .⁴⁰ Upon full discharge the spectrum almost returns to its original state, with however, a particularly notable decrease in the concentration of the S 2s peak as inferred from both photon energies. This finding may be attributed to the formation of a sulfur-deficient phase of the type $\text{Zn}_{1.16}\text{Mo}_6\text{S}_{7.6}$, as shown by XRD data (see Figure 2 and the discussion, *vide supra*). As for S 2p and S 1s, we can notice that the intensity of sulphide (at 226.0 eV and 2469.0 eV) changes significantly while two different oxide forms emerge (at 235.0 eV and ~ 2478 eV) upon zinc insertion/de-insertion (Figure 3(c,d)), respectively. Such changes in the subsurface S 1s manifest electron redistribution between Mo and S and therefore cannot be attributed to surface oxidation by air as initially speculated. Most importantly, the fact that Zn still exists on the subsurface following full discharge (Figure 3e) further demonstrates that Zn ions are trapped in the Mo_6S_8 in line with the electrochemistry data (see above).



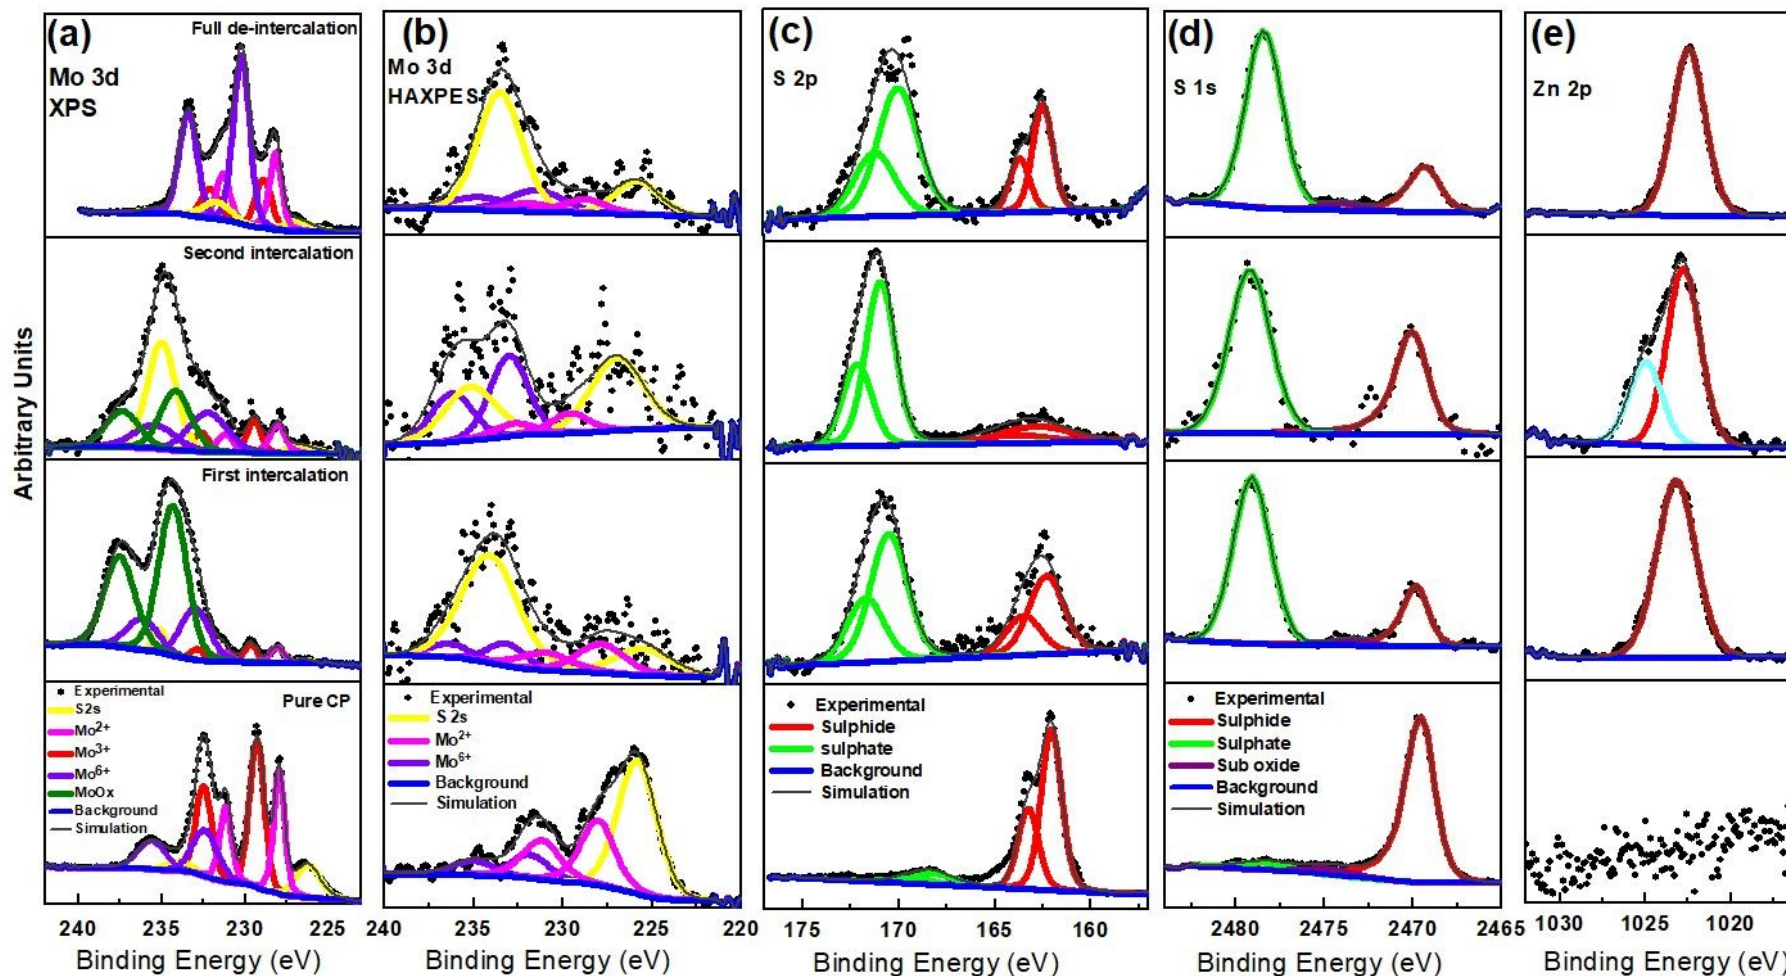


Figure 3. High resolution HAXPES and XPS spectra results of the fully/partially charged and fully discharged Mo_6S_8 electrode in 2M ZnSO_4 half-cell in the region of (a) Mo 3d/S 2s (XPS), (b) Mo 3d/S 2s (HAXPES), (c) S 2p, (d) S 1s (HAXPES), and (e) Zn 2p (HAXPES). Data panels start from bottom to up as follow: Pure CP, First intercalation, second intercalation, and full-deintercalation.



The zinc elemental composition during Zn^{2+} intercalation staging was further examined by means of EDX (Figure S8). From the derived data it is seen that the Zn atomic % increased from 8.42 during the first stage of intercalation (Figure 1b), to 17.53 at complete intercalation (Figure S8c). Interestingly, the fully deintercalated sample contains almost the same percentage of Zn ions as the first intercalation sample, which further confirms zinc trapping. Furthermore, it is worth noting that the theoretical capacity of the sulfur deficient phase $\text{Zn}_{1.16}\text{Mo}_6\text{S}_{7.6}$ is ~ 65.69 mAh/g, a value that aligns closely with both our experimental results (Figure 1d) and the derived discharge capacity recorded following the initial cycles in previous works at nearly equal discharge current.^{18,19}

To further confirm the zinc trapping during the intercalation process, we employed in-situ Raman spectroscopy experiments. Figure 4 shows the fully intercalated/de-intercalated Raman spectra for Mo_6S_8 in 2M ZnSO_4 during the first and second cycle. The free-standing Mo_6S_8 at open-circuit potential (OCP) showed characteristic peaks at 133, 227, 254, 301, 322, 383 and 404 cm^{-1} corresponding to various vibrational modes in Mo_6S_8 .^{21,41} During the zinc intercalation process, the A_{1g} characteristic peak at 404 cm^{-1} becomes broader and the relative intensity ratio of A_{1g}/E_{2g}^1 decreases from 2.67 to 1.32, corresponding to the insertion of Zn^{2+} into the cavities of Mo_6S_8 (Figure 4b). Furthermore, upon Zn intercalation from +0.7 V to +0.17 V vs Zn^{2+}/Zn , the bands soften and the peaks at lower wavenumber almost disappear. Such softening suggests that this mode primarily involves motion of the sulfur atoms, since the force constants between the sulfur atoms are likely to decrease as the sulfur cubes expand, whereas the force constants between the molybdenum atoms should increase as the octahedra shrink.⁴¹ On the other hand, during the discharge process (zinc de-intercalation), the A_{1g} characteristic peak gradually enhances and the relative A_{1g}/E_{2g}^1 intensity ratio increases from 1.32 to 2.32 (Fig.5c). The relative decrease in A_{1g}/E_{2g}^1 intensity after full zinc de-intercalation (2.32) compared to that at the OCP (no zinc intercalation) (2.67), suggests the zinc is trapped inside the Chevrel phase cavities during the first charging process. This could be associated with the formation of the new, sulfur deficient $\text{Zn}_{2.9}\text{Mo}_{15}\text{S}_{19}$ ($\text{Zn}_{1.16}\text{Mo}_6\text{S}_{7.6}$) phase because the force constant between the cubic sulfur atoms decreased with Zn intercalation as previously discussed. Following the first cycle we noted a reversible change of the Raman spectrum, where the ratio between A_{1g}/E_{2g}^1 after the first cycle is almost the same as that of the second cycle, Figure 4(d,e). These results are consistent with the CV data presented in Figure 4a in which the CV plots are reversible following the first cycle. Overall, the analysis of Raman spectra further supports the hypothesis of a quasi-reversible Zn^{2+} ion intercalation/deintercalation mechanism during the first cycle. This results in a decrease in the specific capacity for the second discharge



cycle due to the trapping of zinc during the first cycle. It is worth mentioning that, to the best of our knowledge, no previous studies on zinc ion intercalation into Mo_6S_8 using in-situ Raman spectroscopy have been reported in the literature.

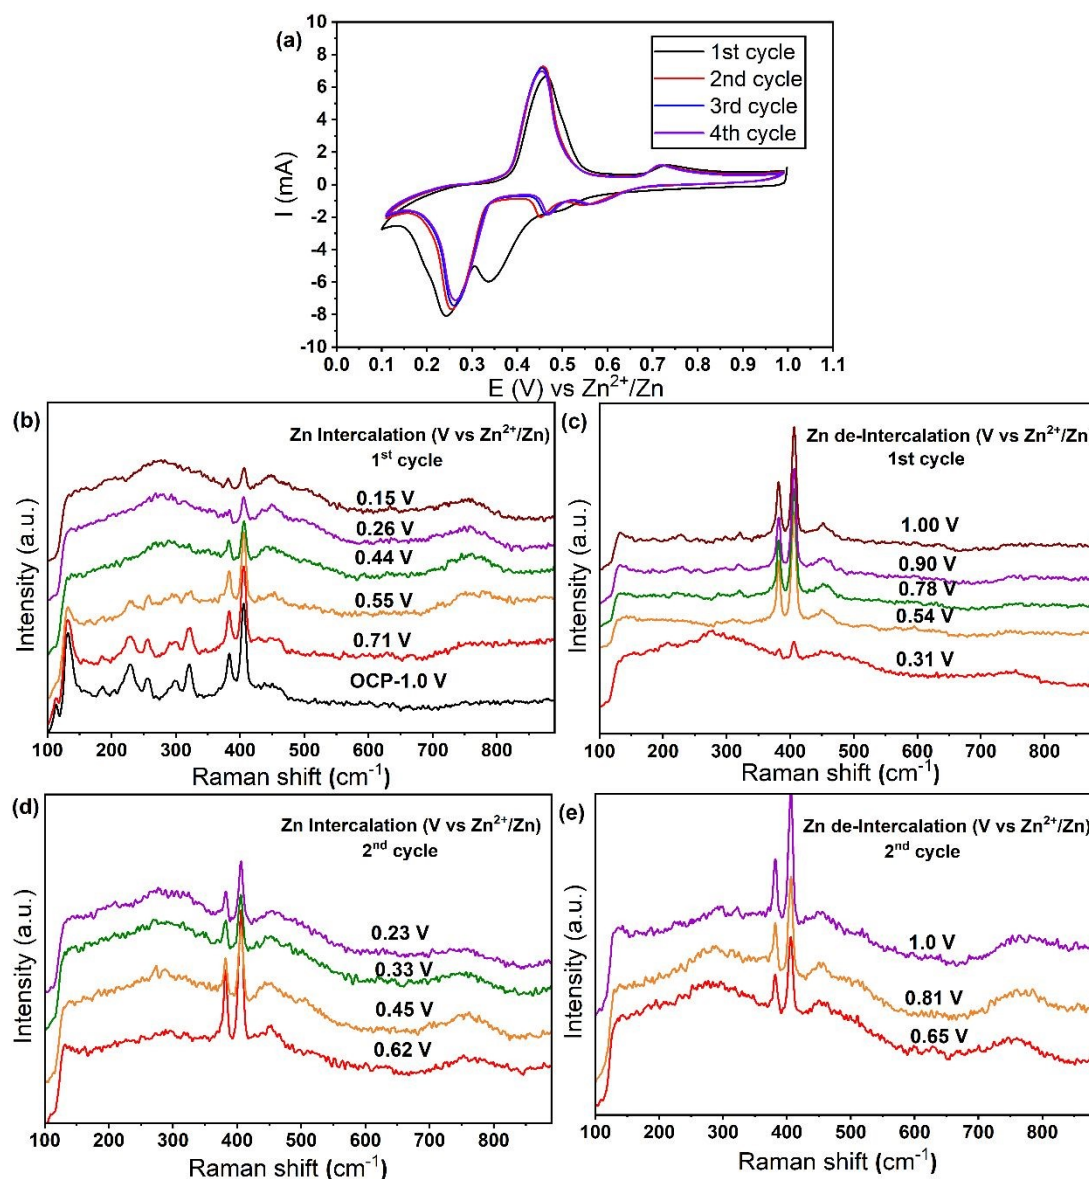


Figure 4. In situ Raman spectral of Mo_6S_8 electrode at different charge and discharge potential in 2M ZnSO_4 . (a) cyclic voltammograms of $\text{Zn}/\text{Mo}_6\text{S}_8$ cell at 1 mV s^{-1} during 1st, 2nd, 3rd, and 4th cycle: (b, c), and (d, e) Raman spectra of the first and second cycle during the intercalation/de-intercalation process, respectively.

To further investigate the potential cause of Zn trapping within the first cycle, we conducted periodic density functional theory (DFT) calculations. As a first possibility we checked for agglomeration within the Mo_6S_8 structure by constructing a $(2 \times 2 \times 3)$ supercell consisting of 12 CP units. This supercell was filled with either two Zn or two Mg atoms at varying distances of one, two, or three unit cells apart (equivalent to approximately 6, 12, and 18 Å, respectively),



and the system energies were compared in order to check whether there is any mutual interaction between the two inserted metal atoms. The energetic differences for both Zn and Mg at all considered distances were in the meV range, which is within the typical DFT accuracy for such systems. Therefore, the DFT calculations suggest that there is no direct interaction between the charge carriers within the Mo₆S₈ structure itself.

We also investigated the possibility of Chevrel phase decomposition into MoS₂ in the form of layered sulfides and compared the formation energies to determine whether the process is thermodynamically feasible. Both zinc and magnesium were considered as potential charge carriers as zinc ions are trapped in the anode, while this behavior is not observed for magnesium. Specifically, we looked at the formation energy per atom of MgMo₂S₄, Mg₂Mo₂S₄, ZnMo₂S₄, and Zn₂Mo₂S₄, as well as their corresponding Chevrel phase counterparts such as MgMo₆S₈ etc. The trends were similar for both charge carriers at one charge carrier per supercell, with a small difference of 0.01 eV/p.a., and the Mg₂Mo₆S₈ being slightly more stable with a difference of 0.05 eV/p.a. These differences are negligible and unlikely to cause significant Zn trapping. Due to the large computational effort associated with the identification of diffusion barriers and the evaluation of their energetic height in such large supercells, we did not determine these barriers. However, in a previous work,⁴² we found a linear dependence of the diffusion barrier on the lattice parameter for the CP. Using the results of this study, we estimate that the diffusion barrier in this system with a lattice constant of 6.43 Å should be of the order of 0.6 eV.

The XRD measurements of Figure 2 suggest the emergence of a Zn_{2.9}Mo₁₅S₁₉ phase during cell cycling. This phase has a different structure from the Chevrel cluster structure, with 4 Zn positions at 100% occupancy (A positions) and 6 positions at 30% occupancy (B positions) which are split into two layers, for a visual representation of the different intercalation positions, refer to Figure S9. With a Zn content of 5.8 (2×2.9) spread over 10 possible sites, we model the phase by incrementally filling 1 to 10 Zn atoms per cell. Note that our unit cell contains two formula units (30 Mo atoms and 38 S atoms), so that increasing the Zn content by one atom at a time results in stoichiometries from Zn_{0.5}Mo₁₅S₁₉ to Zn_{5.0}Mo₁₅S₁₉. The Zn_{3.0}Mo₁₅S₁₉ phase is closest to the experimentally measured Zn content of 2.9 (refer to the XRD data above and the relevant discussion therein). The formation energies of the phase were then examined by filling it with Zn atoms and comparing each phase with n+1 Zn atoms to its previous most stable phase with n Zn atoms. When we fill the empty phase by putting the Zn atoms in the A positions, the formation energies with respect to adding new Zn are positive, which means that it is energetically unfavourable to insert the Zn atom at these sites. This suggests that the B positions are filled first in an empty phase. Here the formation energy is -1.15 eV for the first Zn atom,



regardless of which B position is occupied. For the second Zn the formation energy is -1.18 eV if it is located in a different layer than the first Zn and -0.67 eV if they lie in the same layer. As Figure 1 shows the working window of the battery extends up to ca. 0.8 eV, hence we can surmise that the first two Zn atoms are too strongly bound to be fully deintercalated within the operational window of the battery, which likely results in the observed trapping. For the third Zn atom the formation energy for three Zn atoms in the B positions is only slightly more stable (-0.72 eV) than putting the third Zn atom in one of the 4 A positions (-0.67 eV). For 4 Zn atoms the occupations of 2 Zn in A and 2 in B, 3 in B and 1 in A and all 4 Zn in B are respectively -0.55 , -0.68 and -0.78 eV, making it most favourable for the Zn atoms to be spread equally over the two layers of the B positions (see Figure S9). The configuration with 4 Zn in the B positions and any additional Zn atoms in the A positions is consistently the most stable for Zn content ranging from 5 to 8. The formation energy of this phase always falls within the range of -0.66 to -0.68 eV. The positive formation energies obtained upon attempting to fill the phase beyond an occupancy of 8 Zn atoms suggest that this is the maximum capacity of the phase. The optimal occupancy of Zn atoms in the phase was thus found to be between 1.0 and 4.0 Zn atoms per formula unit, with an equal spread of Zn atoms over the two layers of B positions being the most favourable. The Zn atoms in this range bind to the anode with an energy that enables them to be easily deintercalated within the battery's operating range. In conclusion, our theoretical analysis reveals that during the initial cycle, the $\text{Zn}_{2.9}\text{Mo}_{15}\text{S}_{19}$ phase we examined forms alongside the charged Chevrel phase. However, the phase cannot compete with the CP in terms of reversibility, as it traps 1 Zn atom per formula unit in its structure, while still performing reasonably as an anode by loosely binding 3 additional Zn atoms.

To investigate the diffusion coefficient of zinc ions ($D_{\text{Zn}^{2+}}$) into the Mo_6S_8 cavities, the galvanostatic intermittent titration technique (GITT) was employed (Figure 5), and the $D_{\text{Zn}^{2+}}$ values were calculated according to the following equation:⁴³

$$D_{\text{Zn}^{2+}} = \frac{4}{\pi\tau} \left(\frac{m_B V_M}{M_B S} \right)^2 \left(\frac{\Delta E_s}{\Delta E_t} \right)^2 \quad (2)$$

where τ is the duration of the applied galvanostatic current pulse, m_B , M_B , and V_M are the mass, molecular weight, and molar volume of Mo_6S_8 , respectively. S is the contact area between electrode and electrolyte, while ΔE_s , and ΔE_t are the stabilization (quasi-equilibrium) potential and potential change during galvanostatic current pulse, respectively.

Based on the data derived using equation (2), the profiles of $D_{\text{Zn}^{2+}}$ vs voltage during the intercalation/deintercalation process are displayed in Figure 5(b, d). $D_{\text{Zn}^{2+}}$ values range from



4.99×10^{-7} to 1.07×10^{-10} cm²/s (Zn²⁺ intercalation) and 1.92×10^{-7} to 1.48×10^{-10} cm²/s (Zn²⁺ de-intercalation). The diffusion coefficient data can be divided into two characteristics regions: (i) zinc ion insertion/de-insertion processes and (ii) non-insertion/de-insertion stages. Such phenomena are typical for an intercalation-type battery electrode material.⁴⁴ Initially, from the open circuit voltage (+0.95 V vs Zn²⁺/Zn) to the start of the first insertion plateau (+0.70 V vs Zn²⁺/Zn), the values of $D_{Zn^{2+}}$ are in the range of 7.89×10^{-8} to 2.07×10^{-8} cm²/s. As the intercalation potential increases to +0.47 V vs. Zn²⁺/Zn, $D_{Zn^{2+}}$ increases to 1.0×10^{-7} cm²/s due to the formation of the Zn_xMo₆S₈ phase. In the next stage, the Zn_xMo₆S₈ phase is gradually being transformed to Zn₂Mo₆S₈ as Zn²⁺ intercalation advances (+0.43 to +0.32 V vs. Zn²⁺/Zn) and the determined $D_{Zn^{2+}}$ values lie within the range of 9.6×10^{-8} to 1.07×10^{-10} cm²/s. The decrease in diffusion coefficient upon transformation from Zn_xMo₆S₈ to Zn₂Mo₆S₈ could be correlated to the structural differences between the two phases. In particular, the larger average interatomic distance of Mo-Mo in Zn_xMo₆S₈ (2.71 Å) compared to Zn₂Mo₆S₈ (2.61 Å) may facilitate Zn²⁺ insertion kinetics. Interestingly in the reverse de-intercalation scan, Zn²⁺ diffuses back quickly from the Zn₂Mo₆S₈ phase (1.9×10^{-7} cm²/s) to Zn_xMo₆S₈, which could be due to the reversibility of this process (Zn₂Mo₆S₈) as inferred from the peak separation in cyclic voltammetry data and the increased stability of Zn_xMo₆S₈ relative to Zn₂Mo₆S₈.^{19,45} Following this, nearly identical evolution of diffusion coefficients of Zn²⁺ can be observed as compared to the intercalation process. A detailed list of the calculated diffusion coefficients values at different intercalation/de-intercalation potentials are presented in Table S1 (representative experimental data is presented in Figure S10). It is worth mentioning that the calculated diffusion coefficient values of the nanoscale Mo₆S₈ during charge/discharge process are higher than those of most electrode materials previously reported for aqueous Zn-storage e.g., TiS₂¹³, 1.33×10^{-11} – 5.71×10^{-9} cm²/s; TiSe₂⁷, 10^{-10} – 10^{-9} cm²/s; layered MnO₂⁴⁶, 10^{-14} – 10^{-12} cm²/s; V₂O₅·6H₂O⁴⁷ 10^{-11} – 10^{-10} cm²/s as well as microsized Mo₆S₈-based materials 4.5×10^{-10} – 1.5×10^{-9} cm²/s.⁴⁸ These findings demonstrate the fast kinetics of the prepared Mo₆S₈ driven by the nanosized structure.

Article Online
 DOI: 10.1039/D4NR01238K



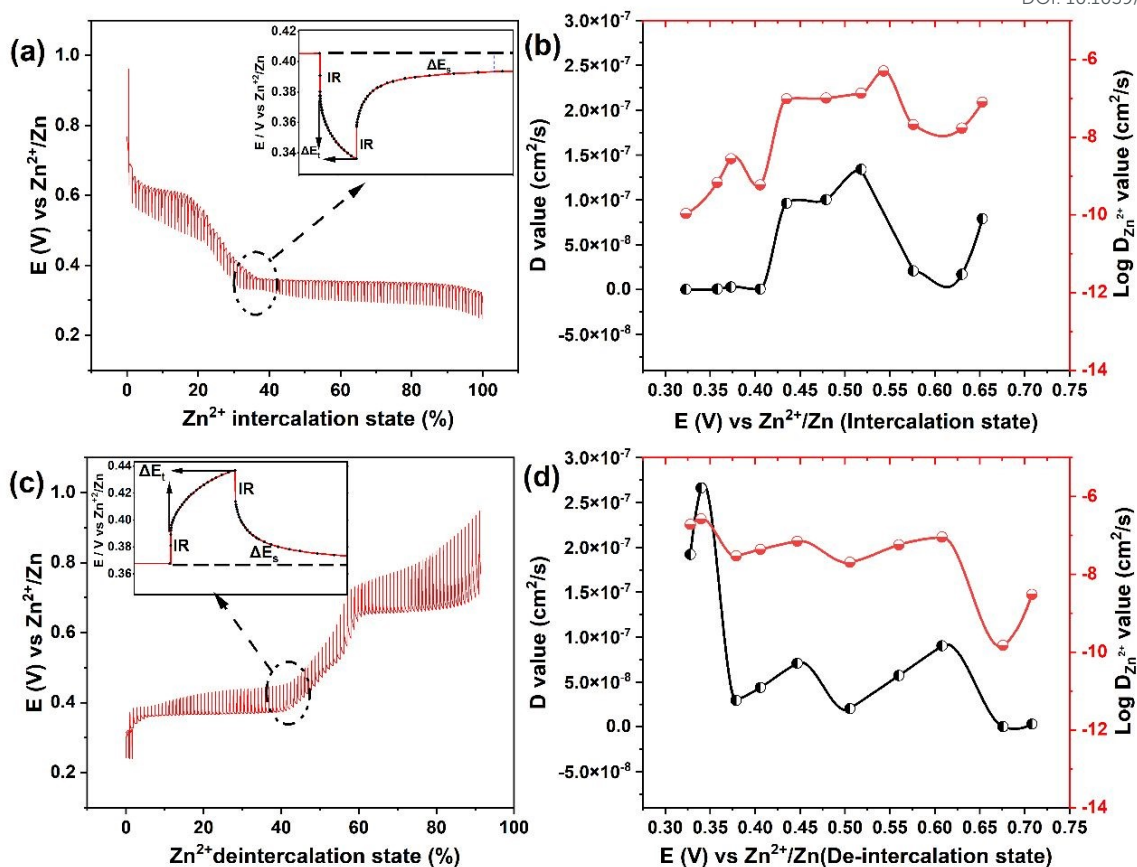


Figure 5. Galvanostatic intermittent titration technique (GITT) curves of in 2M ZnSO_4 at 0.1 A/g recorded during the Zn^{2+} intercalation (a) and deintercalation process (c) as a function of state of (d)intercalation process. The insets in (a, c) scheme for a single step of a GITT experiment. The corresponding Zn^{2+} diffusion coefficients values among the selected steps during intercalation (b) and deintercalation (d) process.

3.3 Characterization of the YEC-8A cathode material in a half-cell

The structural characterisation and the electrochemical performance of activated carbon (YEC-8A) was examined in 2M ZnSO_4 . The XRD pattern (Figure 6a) shows a broad diffraction peak at 43.39° associated with the (101) plane reflection⁴⁹. The broad peak feature of the XRD pattern is indicative of the amorphous structure of the YEC-8A sample. The surface morphology of YEC-8A was examined by SEM (Figure 6b). The activated carbon particles have an irregular shape with a relatively rough surface and particle size within the range of 5 μm to 20 μm . Figure 6(c, d) shows the cyclic voltammograms within a potential window of 1–1.8V vs Zn^{2+}/Zn at various scan rates from 2 to 100 mV/s. The CVs display a quasi-rectangular shape, reflecting the capacitive behaviour of the YEC-8A electrode. The GCD curves (Figure 6e) at different current densities are triangular with negligible IR-drop, implying favourable reversibility and good electrical conductivity of YEC-8A electrode. The specific capacitance



was calculated from the GCD data and presented in Figure 6f. We note that with increasing current density, from 0.2 A/g to 2 A/g, the specific capacitance decreases from ~153 F/g to 113 F/g, respectively (for specific capacitance calculations, refer to the supplementary materials).

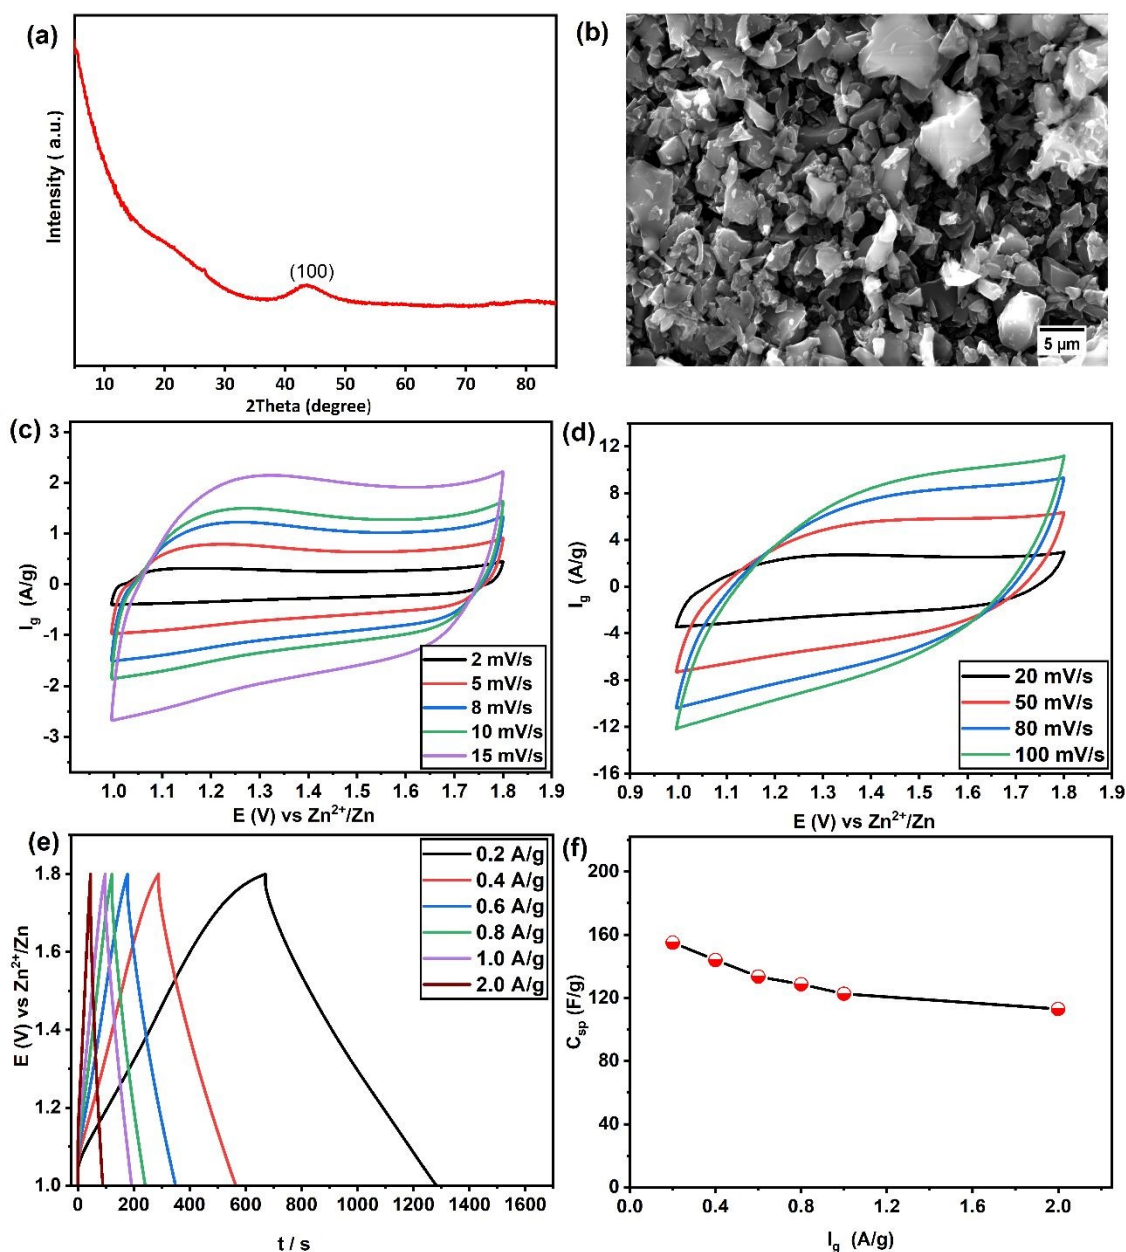


Figure 6. Structural characterisation and electrochemical performance of YEC-8A. (a) XRD pattern; (b) SEM image; (c, d) Cyclic voltammograms as a function of scan rate; (e) GCD curves at current densities from 0.2 to 2 A/g; (f) Specific capacitance as a function of current density.

3.4 Full cell Zn-ion hybrid supercapacitor (ZIHC)

In view of the high performance and fast Zn^{2+} diffusion into Mo_6S_8 , as well as to demonstrate the potential application of the nanoscale synthesised material, we assembled a ZIHC device.



Figure 7a shows the schematic diagram of the assembled ZIHSC, in which Mo_6S_8 , YEC-8A and 2.0 M ZnSO_4 serve as the anode, cathode, and electrolyte, respectively. During the charge/discharge process, zinc ions intercalate/de-intercalate into the anode and reversible ion adsorption/desorption on the YEC-8A cathode surface enables the ZIHSC to repeatedly store/deliver electrical energy. For an ideal symmetric capacitor, the voltage is assumed to be equally divided between both electrodes, since both electrodes have the same mass and amount of charge. In this ZIHSC, however, we have shown that each electrode has a stable potential region and stores a different amount of charge. It is therefore necessary to assemble an optimised, mass-balanced cell in order to maximise the overall performance of the electrochemical ZIHSC.^{50,51} The optimum mass ratio of YEC-8A to Mo_6S_8 electrodes was calculated so as to balance the amount of charge. The charge (Q_{sp}) stored is related to the specific capacity (C_{sp}), the potential evolution at each electrode (ΔV) and the active mass (m) of the corresponding electrode as follows: $Q_{\text{sp}} = m C_{\text{sp}} \Delta V$. Thus, the mass ratio in theory can be further expressed $\frac{m_+}{m_-} = \frac{\Delta V_- * C_{\text{sp}^-}}{\Delta V_+ * C_{\text{sp}^+}}$. As discussed above, the calculated specific capacities of Mo_6S_8 and YEC-8A electrodes are 55 and 31.6 mAh/g at 0.2 A/g; thus, the best mass ratio of cathode to anode was ~ 1.76 . Subsequently, the electrochemical performance of Mo_6S_8 //YEC-8A ZIHSC was evaluated, and the relevant measurements are presented in Figure 8.

The CVs of Mo_6S_8 //YEC-8A within the potential range 0.0–1.6 V at various scan rates from 2 to 12 mV s^{-1} , deviate from the ideal rectangular shape (Figure 7b), suggesting that there are both capacitive and diffusion-controlled energy storage mechanisms.

Trasatti's method⁵² was used to distinguish the surface capacitive and diffusional contribution from the cyclic voltammetric charge plotted as a function of scan rate according to the following equations:^{1,52}

$$Q = Q_{\text{Capacitive}} + Q_{\text{Diffusion}} = Q_{\text{Capacitive}} + K\nu^{-0.5} \quad (3)$$

$$\frac{1}{Q} = \frac{1}{Q_{\text{total}}} + k'\nu^{0.5} \quad (4)$$

$$Q_{\text{Diffusion}} = Q_{\text{total}} - Q_{\text{Capacitive}} \quad (5)$$

where K and k' are constant. $Q_{\text{capacitive}}$ and $Q_{\text{diffusion}}$ represent the surface capacitive and diffusional charge contribution. Q_{total} is the total capacity due to surface and diffusive redox reaction. At a fast scan rate, the capacity contribution due to the diffusion process will be negligible, however, the capacity that is occurring due to the surface process can be treated as constant for different scan rates and hence $Q_{\text{total}} \sim Q_{\text{capacitive}}$. In this case, $Q_{\text{capacitive}}$ can be estimated from the intercept of voltammetric charge (Q) vs. $\nu^{-0.5}$ as shown in Figure 7c. On the



other hand, at a slow scan rate, the whole electrode becomes accessible to electrolyte ions and hence $Q_{\text{total}} \sim Q_{\text{capacitive}} + Q_{\text{diffusion}}$. As a result, the Q_{total} can be obtained from the reciprocal of the intercept of $1/Q$ vs $v^{0.5}$ as presented in Figure 7d. Based on these estimations, Q_{total} , $Q_{\text{capacitive}}$, and $Q_{\text{diffusion}}$ parameters were calculate and are given in Table S2. The diffusion-controlled contribution represents $\sim 79.9\%$ of the total charge storage of the zinc hybrid device and the rest (20.1%) is due to the surface charge storage process, suggesting the intercalation pseudocapacitive mechanism of the fabricated device. We should however emphasize that these percentages are only an approximation as they may vary depending on the scan rates selected.¹

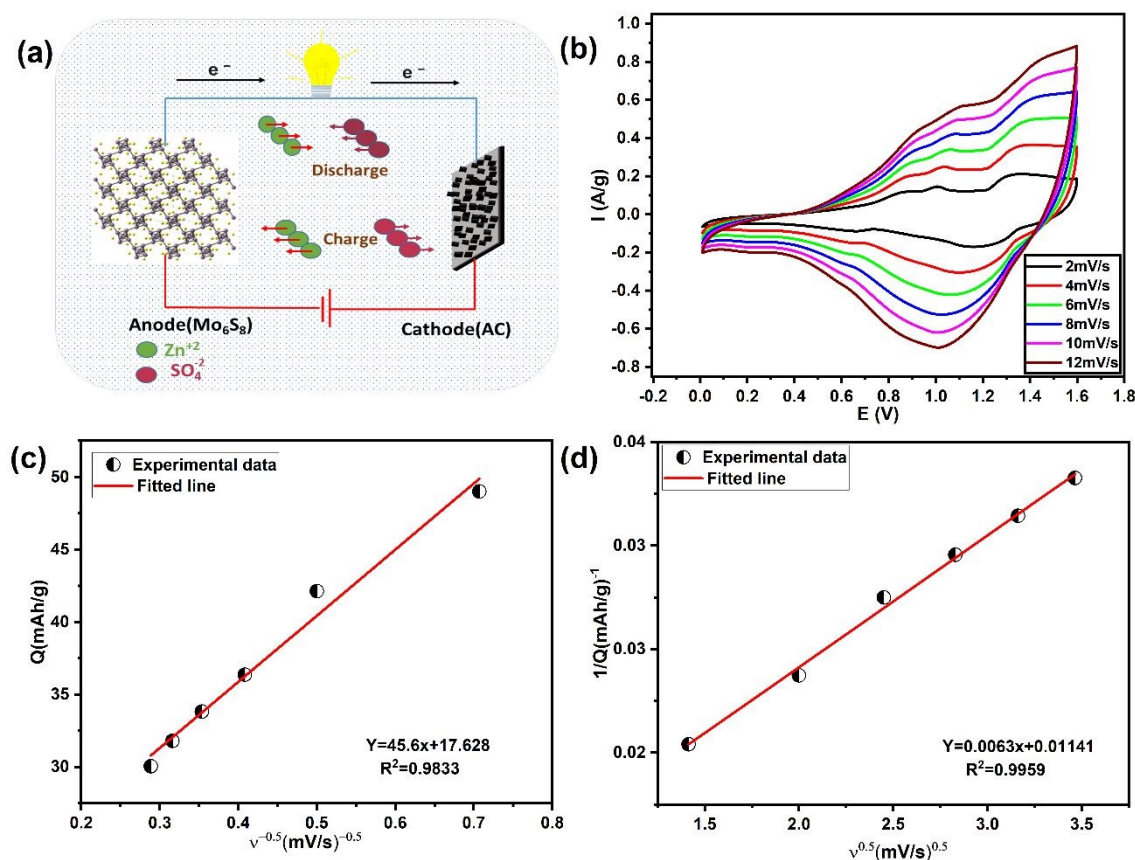


Figure 7. Schematic and charge storage mechanism of the fabricated energy storage system. (a) Schematic diagram of Mo₆S₈/YEC-8A ZIHSC. (b) CVs of Mo₆S₈/YEC-8A at different scan rates from 2 to 12 mV/s. Voltammetric charge (Q) calculated as a function of scan rate according to S. Trasatti method: (c) Q vs $v^{-1/2}$ plot and (d) $1/Q$ vs. $v^{1/2}$ plot.

Figure 8(a,b) shows the GCD plots and rate performance curves of Mo₆S₈//YEC-8A cell, respectively, recorded over a high voltage window of 1.6 V. We can see that the GCD profiles deviate from the capacitive triangular shape, which further demonstrates the simultaneous ionic intercalation/deintercalation and adsorption/desorption energy storage mechanisms. The cell



delivered an average voltage of ~ 1.1 V with an overall capacity of ~ 38 mAh/g, and 19 mAh/g measured at 0.2 and 2 A/g, respectively. This means that the cell maintained 60% of its capacity when the current density was increased by a factor of 10 from 1 to 10 A/g. The decrease in capacity at high current is mainly due to the slow Zn ion interaction into Mo_6S_8 , a behavior related to the battery-type electrode material where more time is needed for the intercalation/deintercalation process. Notably, when the cycling rate returns to 0.2 A/g, the recorded capacity is *ca.* 35.4 mAh/g which corresponds to a capacity retention of *ca.* 90% compared to the first cycle. This observation shows the excellent high-rate performance of the fabricated device.

Figure 8c compares Ragone's plot of the $\text{Mo}_6\text{S}_8/\text{YEC-8A}$ device with other recently published fabricated aqueous hybrid supercapacitors. It can be seen that the maximum specific energy density delivered from our fabricated cell is as high as 43.8 Wh/kg with a power density of 229.9 W/kg at a specific current density of 0.2 A/g. At high current density, of 2 A/g, the device still delivers an energy density of 25.7 Wh/kg with a high-power density of 2250 W/kg. The relatively high specific energy delivered by our device ($\text{Mo}_6\text{S}_8/\text{YEC-8A}$) compared to TiS_2/AC ⁵³ or TiSe_2/AC ⁷, could be due to the high operating voltage of 1.6 V, lower intercalation potential of Zn^{2+} into (*ca.* 0.3 V vs Zn^{2+}/Zn), and hence the high operating voltage of the fabricated device of approximately 1.1 V.

The cycling stability of $\text{Mo}_6\text{S}_8/\text{YEC-8A}$ was tested at 3 A/g for 8000 cycles as shown in Figure 8d. The rapid decrease of capacity during the first cycles may be attributed to the aforementioned trapping of zinc inside the Mo_6S_8 electrode during the initial intercalation process. Following this, the device exhibits high cycling stability with a coulombic efficiency of nearly 100%. More importantly, two assembled $\text{Mo}_6\text{S}_8/\text{YEC-8A}$ coin cells connected in series were able to illuminate the red light-emitting diode as shown in the inset of Figure 8d, demonstrating its practical application. Besides, the EIS spectra of $\text{Mo}_6\text{S}_8/\text{YEC-8A}$ is presented in Figure S11. The intercept of the abscissae (real axis) corresponds to the equivalent series resistance (R_s). This resistance is related to the internal resistance of the electrolyte, electrode material, and contact resistance at the electrode-electrolyte interface. The semicircle in the high to mid-frequency region relates to the charge-transfer process, which represents the zinc ion diffusion resistance during the electrochemical process. The R_s and R_{ct} of the $\text{Mo}_6\text{S}_8/\text{YEC-8A}$ recorded at 1.2 V are, respectively, 1.2 Ω and 6.5 Ω , which again reflects the high conductivity and rapid kinetics of the assembled device.



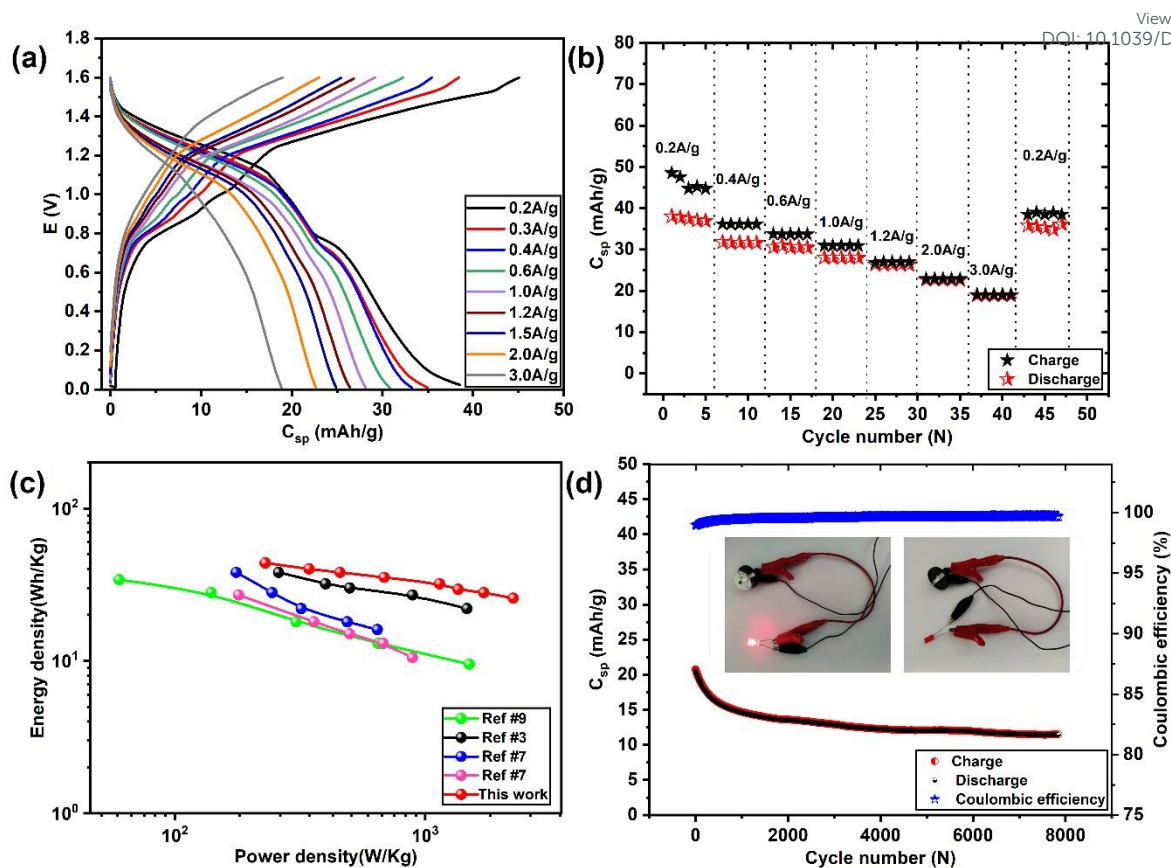


Figure 8. Electrochemical performance of the $\text{Mo}_6\text{S}_8/\text{YEC-8A}$ device in 2 M ZnSO_4 aqueous electrolyte. (a) GCD profiles (E vs. capacity format) recorded at different current densities, (b) corresponding rate capability curves, (c) Ragone's plot comparing $\text{Mo}_6\text{S}_8/\text{YEC-8A}$ device with other recently published ZHSCs, and (d) long-term cycling stability of $\text{Mo}_6\text{S}_8/\text{YEC-8A}$ full cell recorded at a current density of 3 A g^{-1} (inset shows an LED illuminated by a $\text{Mo}_6\text{S}_8/\text{YEC-8A}$ device).

Post-mortem SEM physical characterisation was conducted to investigate the zinc dendrite formation and surface morphology of the cycled Mo_6S_8 , YEC-8A, and zinc electrodes. All investigated electrodes were recovered from the fabricated coin cells, washed thoroughly with water several times, and dried before SEM measurements. Figure 9 shows the surface morphology of YEC-8A, Mo_6S_8 , and zinc electrodes after cycling at 3 A g^{-1} in 2 M ZnSO_4 . We can see that the YEC-8A surface and zinc metal electrodes in $\text{Zn}/\text{YEC-8A}$ device are covered with zinc dendrites (Figure 9(a, b)). In contrast, when Mo_6S_8 is used as the anode in the $\text{Mo}_6\text{S}_8/\text{YEC-8A}$ device, no zinc dendrites are observed on either the anode or cathode surfaces even after 8000 cycles (Figure 9(c, d)). This is attributed to use of a framework material, specifically the Chevrel phase, which provides a “scaffold” into which the reduced form of the metal is held. This selection also depends on the transport Zn ions into the Chevrel phase being



efficient, and the diffusion coefficient being relatively high for divalent ions as concluded from the GITT experiments (as discussed above).

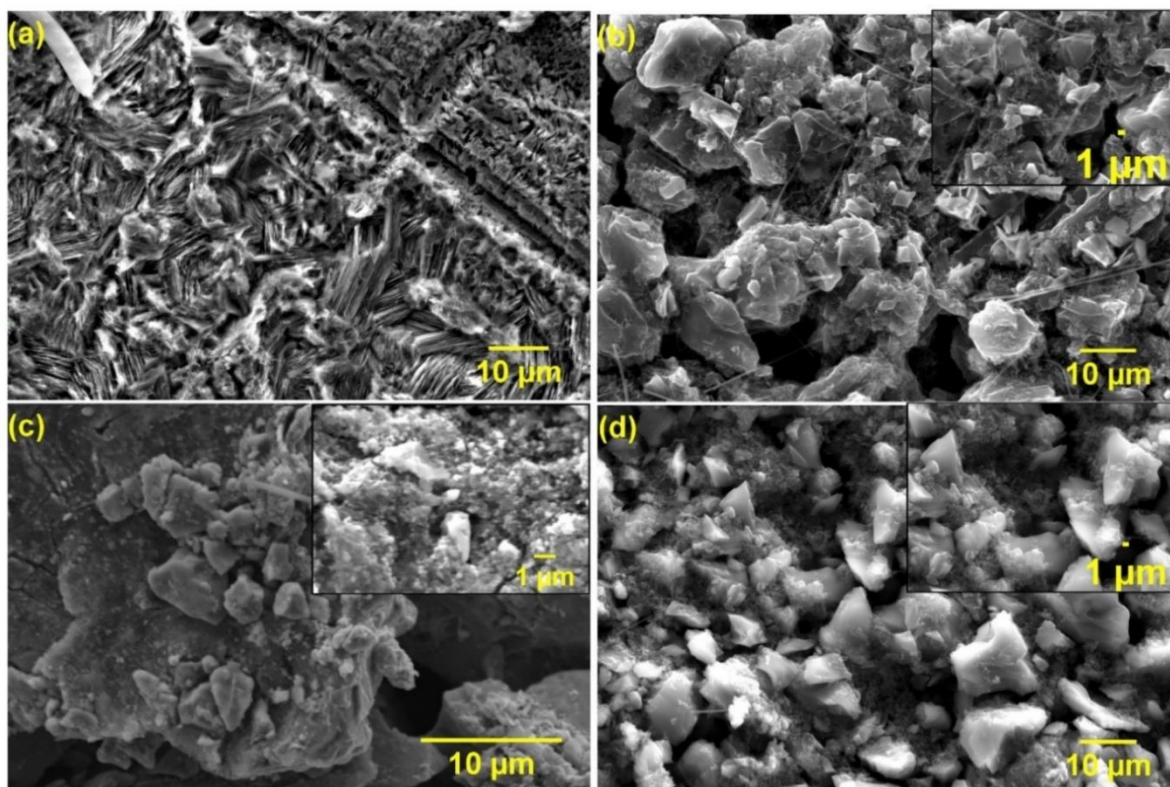


Figure 9. Post-mortem SEM characterization of the electrodes examined after cycling in 2 M ZnSO_4 at a gravimetric current of 3 A g^{-1} . SEM images of (a) zinc foil, and (b) YEC-8A electrode in Zn/YEC-8A system after 100 cycles. SEM images of (c) Mo_6S_8 electrode, and (d) YEC-8A electrode in $\text{Mo}_6\text{S}_8/\text{YEC-8A}$ coin cell after 8000 cycles.

4. Conclusion

We have demonstrated that Mo_6S_8 is a promising dendrite-free zinc anode for ZIHSC devices. A range of electrochemical measurements show that the Mo_6S_8 Chevrel phase follows a multi-step zinc ion intercalation/de-intercalation process, with a lower intercalation potential of approximately 0.3 V vs Zn^{2+}/Zn . Additionally, the nanosized CP offers fast zinc ion kinetics, as inferred by the GITT data, compared to other available anode materials such as TiSe_2 , and TiS_2 . Post-mortem (P-XRD) diffraction shows the formation of a new sulfur deficient $\text{Zn}_{1.16}\text{Mo}_6\text{S}_{7.6}$ phase that tends to be the most stable one upon cycling, as also confirmed theoretically by DFT calculations. Furthermore, in-situ Raman spectroscopy has revealed the change in the phonon structure of the Mo_6S_8 upon intercalation/de-intercalation, indicating zinc trapping upon cycling. In addition, the potential application of nanosized Mo_6S_8 was also



investigated. A ZIHSC device, with a Mo_6S_8 anode and YEC-8A cathode, delivered a capacity of 38 mAh/g, with a superior energy density of 43.8 Wh/kg at a specific current density of 0.2 A/g. In addition, the ZIHSC shows excellent cycling response, up to 8000 cycles (3 A/g) with ~100% coulombic efficiency. Interestingly, the post-mortem SEM analysis show no dendrite formation over the Mo_6S_8 anode compared to the usage of zinc metal. This work provides a proof-of-concept of using Mo_6S_8 compound as zinc-dendrite free anode material for zinc hybrid capacitors. This success could motivate further developments in the adoption of new materials, with lower zinc intercalation potential than the Mo_6S_8 materials demonstrated in this work, for practical application in next-generation ZIHSC energy storage systems.

View Article Online
DOI: 10.1039/D4NR01238K

Conflicts of interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work presented in this paper.

Author Information

Corresponding Authors

*E-mail: david.lewis-4@manchester.ac.uk Tel: +44 (0) 161-306-3561. (D.J.L.)

*E-mail: robert.dryfe@manchester.ac.uk Tel: +44 (0) 161-306-4522. (R.A.W.D).

ORCID

Amr Elgendy: <https://orcid.org/0000-0001-7442-7865>

Athanasios A. Papaderakis: <https://orcid.org/0000-0001-5582-3213>

Alex S. Walton: <https://orcid.org/0000-0002-3207-8406>

Andinet Ejigu: <https://orcid.org/0000-0002-5240-2728>

Ben F. Spencer: <https://orcid.org/0000-0002-1453-5327>

Axel Groß: <https://orcid.org/0000-0003-4037-7331>

David J. Lewis: <https://orcid.org/0000-0001-5950-1350>

Robert A. W. Dryfe: <https://orcid.org/0000-0002-9335-4451>

Acknowledgements

Amr Abdelkader Ahmed Sadek (also known as Amr Elgendy) expresses his gratitude to the Newton-Mosharafa Fund, a partnership between the British Council and the Ministry of Higher Education- Missions Sector in Egypt- for providing him with a full PhD scholarship. Further



support from EPSRC is gratefully acknowledged (EP/T01816X/1). Further support for this work was provided via the Henry Royce Institute, funded through EPSRC grants EP/R00661X/1, EP/P025021/1 and EP/P025498/1.

View Article Online
DOI: 10.1039/D4NR01238K

Data Availability Statement

The data that support the findings of this study are available from the corresponding author upon reasonable request.

References

- 1 V. Augustyn, P. Simon and B. Dunn, *Energy Environ. Sci.*, 2014, **7**, 1597–1614.
- 2 X. Jia, C. Liu, Z. G. Neale, J. Yang and G. Cao, *Chem. Rev.*, 2020, **120**, 7795–7866.
- 3 L. Dong, X. Ma, Y. Li, L. Zhao, W. Liu, J. Cheng, C. Xu, B. Li, Q.-H. Yang and F. Kang, *Energy Storage Mater.*, 2018, **13**, 96–102.
- 4 B. Scrosati, J. Hassoun and Y.-K. Sun, *Energy Environ. Sci.*, 2011, **4**, 3287–3295.
- 5 F. Wang, O. Borodin, T. Gao, X. Fan, W. Sun, F. Han, A. Faraone, J. A. Dura, K. Xu and C. Wang, *Nat. Mater.*, 2018, **17**, 543–549.
- 6 P. He, Q. Chen, M. Yan, X. Xu, L. Zhou, L. Mai and C.-W. Nan, *EnergyChem*, 2019, **1**, 100022.
- 7 L. Wen, Y. Wu, S. Wang, J. Shi, Q. Zhang, B. Zhao, Q. Wang, C. Zhu, Z. Liu and Y. Zheng, *Nano Energy*, 2021, 106896.
- 8 D. Selvakumaran, A. Pan, S. Liang and G. Cao, *J. Mater. Chem. A*, 2019, **7**, 18209–18236.
- 9 X. Ma, J. Cheng, L. Dong, W. Liu, J. Mou, L. Zhao, J. Wang, D. Ren, J. Wu and C. Xu, *Energy Storage Mater.*, 2019, **20**, 335–342.
- 10 Q. Zhang, J. Luan, Y. Tang, X. Ji and H. Wang, *Angew. Chemie Int. Ed.*, 2020, **59**, 13180–13191.
- 11 B. Liu, S. Wang, Z. Wang, H. Lei, Z. Chen and W. Mai, *Small*, 2020, **16**, 2001323.
- 12 Y. Tian, Y. An, C. Wei, B. Xi, S. Xiong, J. Feng and Y. Qian, *Adv. Energy Mater.*, 2021, **11**, 2002529.
- 13 L. Wang, J. Zou, S. Chen, G. Zhou, J. Bai, P. Gao, Y. Wang, X. Yu, J. Li, Y.-S. Hu and H. Li, *Energy Storage Mater.*, 2018, **12**, 216–222.
- 14 T. Xiong, Y. Zhang, Y. Wang, W. S. V. Lee and J. Xue, *J. Mater. Chem. A*, 2020, **8**, 9006–9012.



- 15 Z. Xu, M. Li, W. Sun, T. Tang, J. Lu and X. Wang, *Adv. Mater.*, 2022, **2200077**. View Article Online
DOI: 10.1039/D4NR01238K
- 16 R. Schöllhorn, M. Kümpers and J. O. Besenhard, *Mater. Res. Bull.*, 1977, **12**, 781–788.
- 17 L. Mei, J. Xu, Z. Wei, H. Liu, Y. Li, J. Ma and S. Dou, *Small*, 2017, **13**, 1701441.
- 18 M. S. Chae and S.-T. Hong, *Batteries*, 2019, **5**, 3.
- 19 M. S. Chae, J. W. Heo, S.-C. Lim and S.-T. Hong, *Inorg. Chem.*, 2016, **55**, 3294–3301.
- 20 A. Elgendy, A. A. Papaderakis, R. Cai, K. Polus, S. J. Haigh, A. S. Walton, D. J. Lewis and R. A. W. Dryfe, *Nanoscale*, 2022, **14**, 10125–10135.
- 21 A. Elgendy, A. A. Papaderakis, C. Byrne, Z. Sun, J. V Lauritsen, E. P. C. Higgins, A. Ejigu, R. Cernik, A. S. Walton, D. J. Lewis and R. A. W. Dryfe, *ACS Appl. Energy Mater.*, 2021, **4**, 13015–13026.
- 22 A. Regoutz, M. Mascheck, T. Wiell, S. K. Eriksson, C. Liljenberg, K. Tetzner, B. A. D. Williamson, D. O. Scanlon and P. Palmgren, *Rev. Sci. Instrum.*, 2018, **89**, 73105.
- 23 B. F. Spencer, S. Maniyarasu, B. P. Reed, D. J. H. Cant, R. Ahumada-Lazo, A. G. Thomas, C. A. Muryn, M. Maschek, S. K. Eriksson and T. Wiell, *Appl. Surf. Sci.*, 2021, **541**, 148635.
- 24 N. Fairley, *AES, SIMS More (Casa Softw. Ltd., 2017)*, see www.casaxps.com.
- 25 D. J. H. Cant, B. F. Spencer, W. R. Flavell and A. G. Shard, *Surf. Interface Anal.*, 2022, **54**, 442–454.
- 26 P. Hohenberg and W. Kohn, *Phys. Rev.*, 1964, **136**, B864.
- 27 W. Kohn and L. J. Sham, *Phys. Rev.*, 1965, **140**, A1133.
- 28 H. Euchner and A. Groß, *Phys. Rev. Mater.*, 2022, **6**, 40302.
- 29 G. Kresse and J. Hafner, *Phys. Rev. B*, 1993, **47**, 558.
- 30 G. Kresse and J. Furthmüller, *Phys. Rev. B*, 1996, **54**, 11169.
- 31 G. Kresse and D. Joubert, *Phys. Rev. b*, 1999, **59**, 1758.
- 32 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865.
- 33 P. E. Blöchl, *Phys. Rev. B*, 1994, **50**, 17953.
- 34 M. Mao, Z. Lin, Y. Tong, J. Yue, C. Zhao, J. Lu, Q. Zhang, L. Gu, L. Suo, Y.-S. Hu, H. Li, X. Huang and L. Chen, *ACS Nano*, 2020, **14**, 1102–1110.
- 35 Y. Cheng, L. Luo, L. Zhong, J. Chen, B. Li, W. Wang, S. X. Mao, C. Wang, V. L. Sprenkle and G. Li, *ACS Appl. Mater. Interfaces*, 2016, **8**, 13673–13677.
- 36 E. Levi, G. Gershinsky, D. Aurbach and O. Isnard, *Inorg. Chem.*, 2009, **48**, 8751–8758.
- 37 J. Huang, Z. Wang, M. Hou, X. Dong, Y. Liu, Y. Wang and Y. Xia, *Nat. Commun.*, 2018, **9**, 2906.
- 38 P. Yan, J. Zheng, J. Liu, B. Wang, X. Cheng, Y. Zhang, X. Sun, C. Wang and J.-G.



- Zhang, *Nat. energy*, 2018, **3**, 600–605.
- 39 Y. Tong, A. Gao, Q. Zhang, T. Gao, J. Yue, F. Meng, Y. Gong, S. Xi, Z. Lin and M. Mao, *Energy Storage Mater.*, 2021, **37**, 87–93.
- 40 J. Zou and G. L. Schrader, *J. Catal.*, 1996, **161**, 667–686.
- 41 D. J. Holmgren, R. T. Demers, M. V Klein and D. M. Ginsberg, *Phys. Rev. B*, 1987, **36**, 1952–1955.
- 42 K. Helmbrecht, H. Euchner and A. Groß, *Batter. Supercaps*, 2022, **5**, e202200002.
- 43 W. Weppner and R. A. Huggins, *J. Electrochem. Soc.*, 1977, **124**, 1569.
- 44 P. Li, X. Zheng, H. Yu, G. Zhao, J. Shu, X. Xu, W. Sun and S. X. Dou, *Energy Storage Mater.*, 2019, **16**, 512–518.
- 45 E. Gocke, W. Schramm, P. Dolscheid and R. Scho, *J. Solid State Chem.*, 1987, **70**, 71–81.
- 46 B. Lee, H. R. Lee, H. Kim, K. Y. Chung, B. W. Cho and S. H. Oh, *Chem. Commun.*, 2015, **51**, 9265–9268.
- 47 N. Zhang, M. Jia, Y. Dong, Y. Wang, J. Xu, Y. Liu, L. Jiao and F. Cheng, *Adv. Funct. Mater.*, 2019, **29**, 1807331.
- 48 E. Levi, G. Gershinsky, D. Aurbach, O. Isnard and G. Ceder, *Chem. Mater.*, 2009, **21**, 1390–1399.
- 49 S. Ghosh, R. Santhosh, S. Jeniffer, V. Raghavan, G. Jacob, K. Nanaji, P. Kollu, S. K. Jeong and A. N. Grace, *Sci. Rep.*, 2019, **9**, 1–15.
- 50 E. Redondo, L. W. Le Fevre, R. Fields, R. Todd, A. J. Forsyth and R. A. W. Dryfe, *Electrochim. Acta*, 2020, **360**, 136957.
- 51 A. Elgendy, N. M. El Basiony, F. E.-T. Heakal and A. E. Elkholy, *J. Power Sources*, 2020, **466**, 228294.
- 52 S. Ardizzone, G. Fregonara and S. Trasatti, *Electrochim. Acta*, 1990, **35**, 263–267.
- 53 Q. Wang, S. Wang, J. Li, L. Ruan, N. Wei, L. Huang, Z. Dong, Q. Cheng, Y. Xiong and W. Zeng, *Adv. Electron. Mater.*, 2020, **6**, 2000388.

View Article Online
DOI: 10.1039/D4NR01238K

